

Report Documentation Page				Form Approved OMB No. 0704-0188	
Public reporting burden for the collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington VA 22202-4302. Respondents should be aware that notwithstanding any other provision of law, no person shall be subject to a penalty for failing to comply with a collection of information if it does not display a currently valid OMB control number.					
1. REPORT DATE 2008		2. REPORT TYPE		3. DATES COVERED 00-00-2008 to 00-00-2008	
4. TITLE AND SUBTITLE Carbon Surface Modification for Enhanced Corrosion Resistance				5a. CONTRACT NUMBER	
				5b. GRANT NUMBER	
				5c. PROGRAM ELEMENT NUMBER	
6. AUTHOR(S)				5d. PROJECT NUMBER	
				5e. TASK NUMBER	
				5f. WORK UNIT NUMBER	
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) Naval Research Laboratory, 4555 Overlook Avenue SW, Washington, DC, 20375				8. PERFORMING ORGANIZATION REPORT NUMBER	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES)				10. SPONSOR/MONITOR'S ACRONYM(S)	
				11. SPONSOR/MONITOR'S REPORT NUMBER(S)	
12. DISTRIBUTION/AVAILABILITY STATEMENT Approved for public release; distribution unlimited					
13. SUPPLEMENTARY NOTES					
14. ABSTRACT					
15. SUBJECT TERMS					
16. SECURITY CLASSIFICATION OF:			17. LIMITATION OF ABSTRACT Same as Report (SAR)	18. NUMBER OF PAGES 2	19a. NAME OF RESPONSIBLE PERSON
a. REPORT unclassified	b. ABSTRACT unclassified	c. THIS PAGE unclassified			

Carbon Surface Modification for Enhanced Corrosion Resistance

P.M. Natishan,¹ F.J. Martin,¹ E.J. Lemieux,¹
T.M. Newbauer,² R. Rayne,¹ and R.A. Bayles¹

¹Chemistry Division

²SAIC

Introduction: Case hardening by carburization has long been recognized to produce wear-resistant surfaces in steels. Historically, case hardening has not been applicable to chromium-containing alloys such as stainless steels (SS), due to chromium carbide formation that significantly degraded corrosion performance. As a result, the availability of case-hardened (and consequently wear-resistant) alloys for applications in corrosive environments was extremely limited. A new low-temperature (450°–500 °C) paraequilibrium carburization technique has been developed for introducing carbon into stainless steel surfaces without formation of carbides.^{1,2} This surface modification technique has been termed Low-Temperature Colossal Supersaturation (LTCSS). Paraequilibrium refers to the concept that the diffusion of substitutional solutes (metal atoms, such as Cr and Ni in the alloy) is slower than the diffusion of interstitial solutes (atoms such as carbon, that fit between metal alloy atoms). Substitutional solutes are effectively immobile under LTCSS treatment conditions, whereas carbon can diffuse considerable distances into the alloy. These interstitially hardened surfaces constitute a new branch of engineered materials, in which improved corrosion resistance is attained alongside improvements in wear and fatigue resistance.

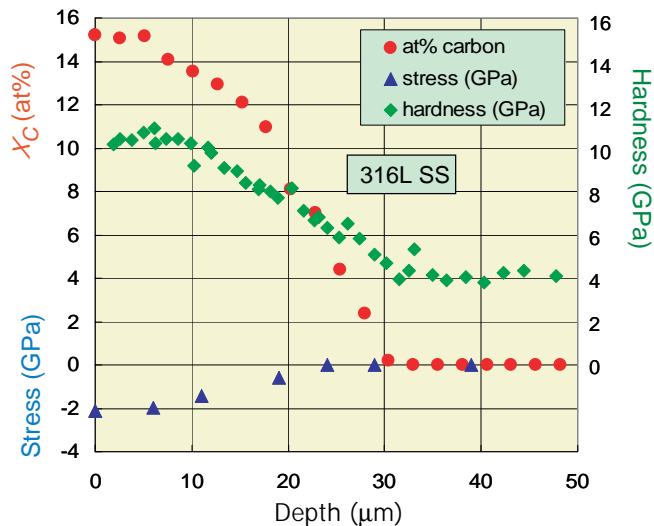
Improved Surface Hardness: The effect of LTCSS treatment on austenitic stainless steels has been shown to dramatically increase surface hardness through residual compressive surface stress (important for fatigue resistance and wear resistance). Figure 1 shows the surface carbon concentrations, residual surface stresses, and hardness resulting from LTCSS treatment. Carbon concentrations of up to 15 atomic percent can be generated in the near-surface region encasing the entire treated component. The large concentration of interstitial carbon induces a lattice expansion that results in surface compressive stresses greater than 2 GPa (300 ksi). These large residual compressive stresses significantly enhance the high cycle fatigue endurance limit,² increasing the service life of the material. Increasing the surface hardness of the material increases wear resistance. Near-surface Vickers microhardness values (HV) of 1200 HV have been obtained on LTCSS-treated 316L SS, representing a significant increase in surface hardness over the substrate material (Vickers 300 HV). To give some perspective,

environmentally unfavorable hard chrome coatings are frequently used on critical aircraft components to increase wear resistance, where surface hardnesses can reach as high as 1100 HV. Thus a LTCSS-treated 316 SS has a surface hardness that rivals the best hard chrome coating. A surprising feature of LTCSS treatment is that the inherently good ductility of the base material is retained in the treated surface.² Additional positive attributes of LTCSS include no net dimensional changes in treated components, treatment of all exposed surfaces, and the ability to batch process large numbers of components at once.

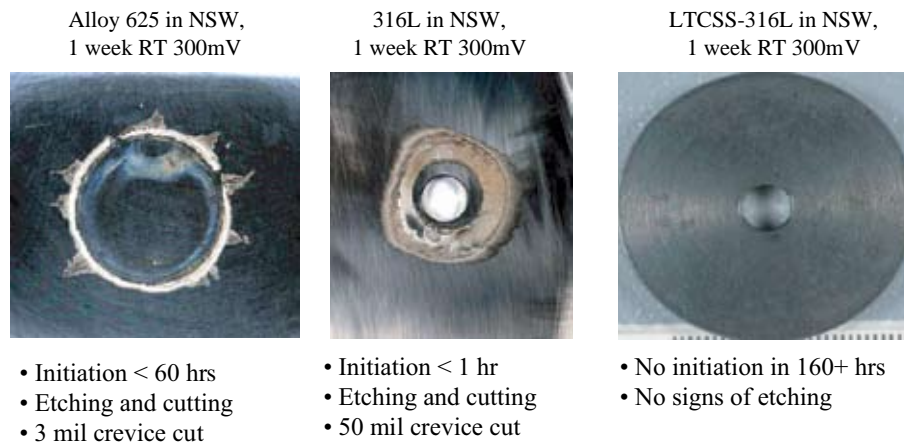
Pitting Corrosion Resistance: Electrochemical testing at NRL to determine pitting corrosion resistance³ has shown that there is dramatic increase in the pitting resistance of the LTCSS-treated 316 SS when compared to the untreated material. LTCSS treatment increased pitting potential from +320 millivolts (mV) for untreated material to +950 mV for the LTCSS-treated material.⁴ The pitting potential is an electrochemical parameter used in laboratory testing to compare the pitting resistance of materials; a high positive value is desired. This is a dramatic increase in pitting corrosion resistance such that under practical conditions experienced in natural seawater (NSW) environments, LTCSS-treated 316 SS is virtually immune to pitting corrosion.

Crevice Corrosion Resistance: Crevice corrosion resistance is another aspect of corrosion behavior of particular interest to the Navy. Comparison of crevice corrosion resistance for untreated 316L SS and LTCSS-treated 316L is presented in Fig. 2. Crevice corrosion damage on an untreated 316L coupon following one week of crevice exposure is shown in the center of the figure. LTCSS-modified 316L (far right) did not initiate crevice corrosion under these exposure conditions (+300 mV, ambient temperature seawater) during the one-week test. Figure 2 also includes results published for Alloy 625 (left photo, an exotic Ni-22Cr-9Mo superalloy) for the same test conditions and crevice cell design.³ These results indicate that the corrosion resistance of LTCSS-treated 316L was greatly increased compared to the untreated 316 and the more expensive, high-grade Ni alloy.

Summary: Low-Temperature Colossal Supersaturation is a process for introducing carbon in excess of 15 atomic percent into stainless steels without formation of carbides. The results of the NRL work show that LTCSS treatment dramatically improved the localized corrosion resistance (both pitting and crevice corrosion) of 316L austenitic SS in ambient temperature seawater. LTCSS treatment has the potential to be applied to a multitude of alloys already used by the Navy. This

**FIGURE 1**

Carbon concentration, surface hardness, and residual stress profiles for LTCSS-modified 316L stainless steel (from Ref. 2).

**FIGURE 2**

Photographs of crevice corrosion specimens after testing (RT = run time). Unmodified 316L SS (center) and LTCSS-modified 316L SS (right) after week-long ambient seawater (NSW) crevice corrosion testing at +300 mV. At left, Alloy 625 (high-grade Ni-Cr-Mo alloy) exposed to similar conditions (from Ref. 3).

in turn would increase the service life of components and increase readiness and availability of naval assets. In addition, LTCSS-treated surfaces, in most cases, have hardness values greater than hard chrome and thus present a potential alternative to this environmentally undesirable, toxic, wear-resistant and corrosion-resistant coating.

Acknowledgments: The authors gratefully acknowledge Dr. Airan Perez of the Office of Naval Research for financial support and technical direction of this work. The authors also wish to thank Mr. Peter Williams and Dr. Sunniva Collins of Swagelok Company (Solon, OH) for significant technical assistance and for performing LTCSS treatments of the stainless steel coupons employed in this work. The authors also acknowledge G.M. Michal, F. Ernst, H.

Kahn, and A.H. Heuer of Case Western University for many stimulating discussions.

[Sponsored by ONR]

References

- ¹ P.C. Williams and S.V. Marx, Swagelok Company, Low-Temperature Case-Hardening Processes, U.S. patent 6,093,303 (July 25, 2000).
- ² G.M. Michal, F. Ernst, H. Kahn, Y. Cao, F. Oba, N. Agarwal, and A.H. Heuer, "Carbon Supersaturation due to Paraequilibrium Carburation: Stainless Steels with Greatly Improved Mechanical Properties," *Acta Materialia* **54**, 1597-1606 (2006).
- ³ F.J. Martin, P.M. Natishan, K.E. Lucas, E.A. Hogan, A.M. Grolleau, and E.D. Thomas, "Crevice Corrosion of Alloy 625 in Natural Seawater," *Corrosion* **59**, 498-504 (2003).
- ⁴ E.J. Martin, E.J. Lemieux, T.M. Newbauer, R.A. Bayles, P.M. Natishan, H. Kahn, G.M. Michal, F. Ernst, and A.H. Heuer, "Carburization-Induced Passivity of 316 L Austenitic Stainless Steel," *Electrochemical and Solid-State Letters* **10**, C76 (2007). ★